

Keene, T.D., Hursthouse, M.B., and Price, D.J. (2006)
Poly[methylamine- μ -oxalato-copper(II)]. *Acta Crystallographica*.
Section E: Structure Reports Online, 62 (6). M1373-M1375. ISSN 1600-
5368

<http://eprints.gla.ac.uk/12189>

Deposited on: 4 October 2012

Poly[methylamine- μ -oxalato-copper(II)]

Tony D. Keene,^a
Michael B. Hursthouse^b and
Daniel J. Price^{a*}

^aWestCHEM, Department of Chemistry,
University of Glasgow, University Avenue,
Glasgow G12 8QQ, Scotland, and ^bSchool
of Chemistry, University of Southampton,
Highfield, Southampton SO17 1BJ, England

Correspondence e-mail:
danielp@chem.gla.ac.uk

Key indicators

Single-crystal X-ray study
 $T = 566$ K
Mean $\sigma(\text{C}—\text{C}) = 0.008$ Å
 R factor = 0.057
 wR factor = 0.130
Data-to-parameter ratio = 15.5

For details of how these key indicators were
automatically derived from the article, see
<http://journals.iucr.org/e>.


The six-coordinate copper(II) ions in the title compound, $[\text{Cu}(\text{C}_2\text{O}_4)(\text{CH}_3\text{N})]$, experience a Jahn–Teller distortion. The structure is a two-dimensional coordination network, with three crystallographically independent oxalate ions, two of them centrosymmetric, bridging Cu^{II} ions in three different coordination modes. Each Cu ion is also coordinated by methylamine which is involved in both intra- and interlayer hydrogen bonding.

Received 2 May 2006

Accepted 5 May 2006

Comment

The oxalate ligand is known for its chelating and bridging coordination modes. It is used by magnetochemists to mediate significant exchange interactions and can result in magnetically ordered materials (Coronado *et al.*, 2000; Decurtins *et al.*, 1993; Demunno *et al.*, 1995; Hursthouse *et al.*, 2004; Julve *et al.*, 1984; Keene *et al.*, 2004; Mathoniere *et al.*, 1996; Price *et al.*, 2001). We present here the structure of $[\text{Cu}(\text{ox})(\text{CH}_3\text{NH}_2)]$ (ox = oxalate), (I).

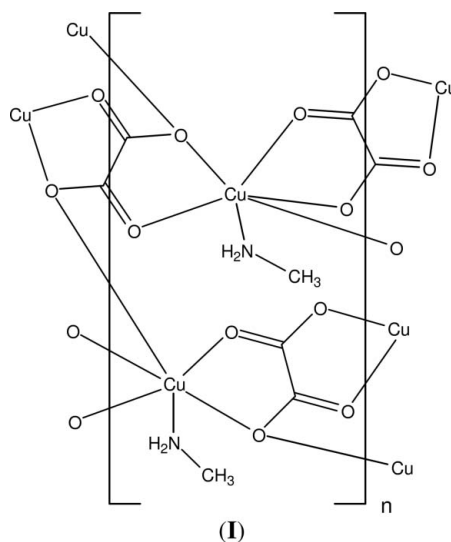

The asymmetric unit of (I) contains two Cu atoms, two methylamine molecules, and one complete and two halves of oxalate anions (Fig. 1). The Cu^{II} cations each have a CuNO_5 coordination and show a large Jahn–Teller-induced tetragonal elongation. While the coordination environment of each Cu^{II} ion is very similar (Table 1), the coordination of the three oxalate ions differs significantly (Fig. 2). The structure of (I) is a complex two-dimensional coordination network that can best be viewed by initially considering only the short Cu—O/N contacts (<2.05 Å). The structure is built from two distinct copper oxalate chains. Chain A (Fig. 3) is formed from Cu1 and the oxalate containing C1 and C2; it consists of a simple

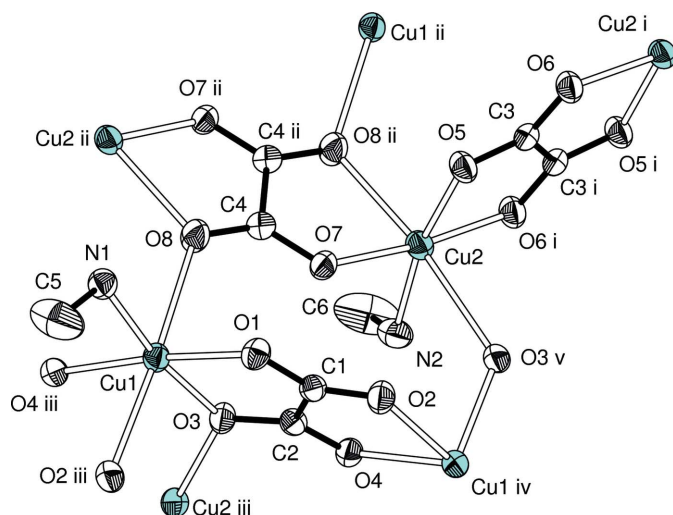
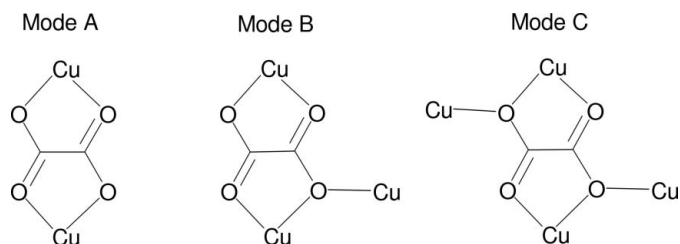
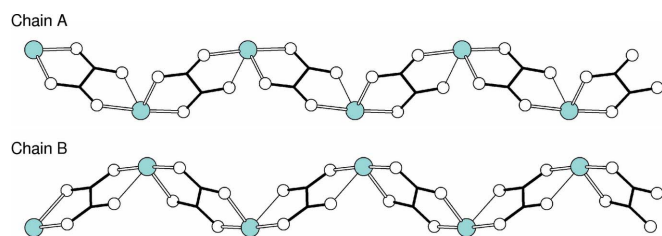
**Figure 1**

Fig. 1. The asymmetric unit of (I) and selected symmetry-equivalent atoms, showing the coordination of both metal ions and ligands. Displacement ellipsoids are drawn at the 40% probability level and H atoms have been omitted for clarity. [Symmetry codes: (i) $1 - x, -y, -z$; (ii) $1 - x, -y, 1 - z$; (iii) $x, \frac{1}{2} - y, \frac{1}{2} + z$; (iv) $x, \frac{1}{2} - y, -\frac{1}{2} + z$].

**Figure 2**

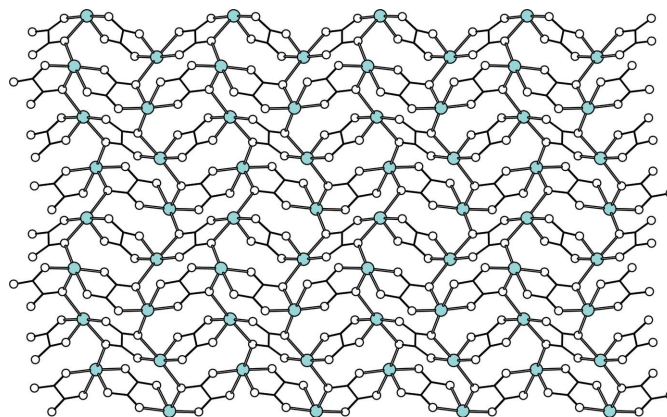
Schematic illustration of the three oxalate coordination modes seen in (I).

**Figure 3**

Two types of copper oxalate chain (A top and B bottom) from which the extended structure is built.

alternation of these components, with a $[-\text{Cu1}-\text{oxB}]_n$ repeat unit and a $\text{Cu} \cdots \text{Cu}$ separation of 5.530 (3) Å. Chain B (Fig. 3) is built from Cu2 and the crystallographically centrosymmetric oxalate anions containing C3 and C4. It has a more complex topology with a $[-\text{Cu2}-\text{oxA}-\text{Cu2}-\text{oxC}]_n$ repeat unit and alternating $\text{Cu} \cdots \text{Cu}$ separations of 5.537 (9) and 5.192 (9) Å. The longer Cu—O interactions link neighbouring chains into a corrugated two-dimensional structure in the *bc* plane (Fig. 4). The coordinated methylamine displays both intra- and inter-layer hydrogen bonding (Table 2).

Surprisingly, there are very few structures that contain copper and either methyl- or ethylamine. Chemically, the most

**Figure 4**

The complex two-dimensional Cu(ox) network, viewed along the *a* axis.

similar compound with a known structure is $[\text{Cu}(\text{NH}_3)(\text{ox})]$ (Cavalca *et al.*, 1972). Indeed, the structure of this compound shows remarkable similarity to that of (I). $[\text{Cu}(\text{NH}_3)(\text{ox})]$ also has a two-dimensional character, being built from Cu(ox) chains with the type B structure described above. Here, neighbouring chains are linked through the long Cu—O interactions into a two-dimensional sheet structure, with a topology that is different from that seen in (I).

Experimental

Single crystals of (I) were synthesized by dissolving synthetic mooloolite, *viz.* $[\text{Cu}(\text{ox})] \cdot 0.33\text{H}_2\text{O}$ (1.000 g, 6.35 mmol), in an aqueous methylamine solution (20 ml, 40% *w/w*). The resultant dark-blue solution was further diluted with distilled water to a volume of 100 ml and left to evaporate. Blue crystals of (I) formed as a minor product amongst a large proportion of finely divided $[\text{Cu}(\text{ox})] \cdot 0.33\text{H}_2\text{O}$.

Crystal data

$[\text{Cu}(\text{C}_2\text{O}_4)(\text{CH}_3\text{N})]$
 $M_r = 365.24$
 Monoclinic, $P2_1/c$
 $a = 9.421$ (8) Å
 $b = 12.668$ (12) Å
 $c = 9.392$ (7) Å
 $\beta = 102.53$ (7)°
 $V = 1094.1$ (16) Å³

$Z = 4$
 $D_x = 2.217$ Mg m⁻³
 Mo $K\alpha$ radiation
 $\mu = 3.92$ mm⁻¹
 $T = 293$ (2) K
 Block, blue
 $0.04 \times 0.03 \times 0.03$ mm

Data collection

Nonius KappaCCD diffractometer
 φ and ω scans
 Absorption correction: multi-scan
 (SADABS; Sheldrick, 2003)
 $T_{\min} = 0.859$, $T_{\max} = 0.891$

11196 measured reflections
 2525 independent reflections
 1816 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.076$
 $\theta_{\max} = 27.7^\circ$

Refinement

Refinement on F^2
 $R[F^2 > 2\sigma(F^2)] = 0.057$
 $wR(F^2) = 0.130$
 $S = 1.08$
 2525 reflections
 163 parameters
 H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0482P)^2 + 2.4064P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} < 0.001$
 $\Delta\rho_{\max} = 0.53$ e Å⁻³
 $\Delta\rho_{\min} = -0.79$ e Å⁻³

Table 1

Selected geometric parameters (Å, °).

Cu1—O1	1.955 (4)	Cu2—O7	1.967 (4)
Cu1—N1	1.992 (5)	Cu2—N2	1.974 (5)
Cu1—O4 ⁱ	2.004 (4)	Cu2—O5	1.994 (4)
Cu1—O3	2.025 (4)	Cu2—O6 ⁱⁱ	2.002 (4)
Cu1—O2 ⁱ	2.307 (4)	Cu2—O8 ⁱⁱⁱ	2.311 (4)
O1—Cu1—N1	91.98 (18)	O7—Cu2—N2	92.53 (19)
N1—Cu1—O4 ⁱ	91.02 (17)	O7—Cu2—O5	93.08 (16)
O1—Cu1—O3	83.91 (15)	N2—Cu2—O6 ⁱⁱ	90.85 (18)
O4 ⁱ —Cu1—O3	93.74 (15)	O5—Cu2—O6 ⁱⁱ	84.50 (16)
O1—Cu1—O2 ⁱ	97.03 (15)	O7—Cu2—O8 ⁱⁱⁱ	78.20 (15)
N1—Cu1—O2 ⁱ	98.67 (18)	N2—Cu2—O8 ⁱⁱⁱ	100.3 (2)
O4 ⁱ —Cu1—O2 ⁱ	78.06 (15)	O5—Cu2—O8 ⁱⁱⁱ	89.80 (18)
O3—Cu1—O2 ⁱ	89.74 (16)	O6 ⁱⁱ —Cu2—O8 ⁱⁱⁱ	95.65 (16)

Symmetry codes: (i) $x, -y + \frac{1}{2}, z + \frac{1}{2}$; (ii) $-x + 1, -y, -z$; (iii) $-x + 1, -y, -z + 1$; (iv) $x, -y + \frac{1}{2}, z - \frac{1}{2}$.**Table 2**

Hydrogen-bond geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
N1—H1A \cdots O1 ^v	0.9	2.22	3.042 (7)	153
N1—H1B \cdots O6 ^{vi}	0.9	2.39	3.256 (7)	161
N2—H2B \cdots O4	0.9	2.42	3.137 (7)	137

Symmetry codes: (v) $-x, -y, -z + 1$; (vi) $x, y, z + 1$.

H atoms were positioned geometrically, with N—H = 0.90 Å for amine H and C—H = 0.96 Å for methyl H atoms, and were constrained to ride on their parent atoms, with $U_{\text{iso}}(\text{H}) = xU_{\text{eq}}(\text{C}, \text{N})$, where $x = 1.2$ for amine H and $x = 1.5$ for methyl H atoms.

Data collection: *DENZO* (Otwinowski & Minor, 1997) and *COLLECT* (Hoof, 1998); cell refinement: *DENZO* and *COLLECT*; data reduction: *DENZO* and *COLLECT*; program(s) used to solve

structure: *SIR92* (Altomare *et al.*, 1993) in *WinGX* (Farrugia, 1999); program(s) used to refine structure: *SHELXS97* (Sheldrick, 1997) in *WinGX*; molecular graphics: *DIAMOND* (Brandenburg, 1999).

The authors are grateful to the EPSRC, the University of Glasgow and the University of Southampton for financial support.

References

- Altomare, A., Cascarano, G., Giacovazzo, C. & Guagliardi, A. (1993). *J. Appl. Cryst.* **26**, 343–350.
- Brandenburg, K. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Cavalca, L., Tomlinso, A. A., Villa, A. C., Manfredo, A. G. & Mangia, A. (1972). *J. Chem. Soc. Dalton Trans.* pp. 391–398.
- Coronado, E., Galan-Mascaros, J. R., Gomez-Garcia, C. J. & Laukhin, V. (2000). *Nature (London)*, **408**, 447–449.
- Decurtins, S., Schmale, H. W., Schneuwly, P. & Oswald, H. R. (1993). *Inorg. Chem.* **32**, 1888–1892.
- Demunno, G., Ruiz, R., Lloret, F., Faus, J., Sessoli, R. & Julve, M. (1995). *Inorg. Chem.* **34**, 408–411.
- Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
- Hoof, R. (1998). *COLLECT*. Nonius BV, Delft, The Netherlands.
- Hursthouse, M. B., Light, M. E. & Price, D. J. (2004). *Angew. Chem. Int. Ed.* **43**, 472–475.
- Julve, M., Verdager, M., Gleizes, A., Philochelevisalles, M. & Kahn, O. (1984). *Inorg. Chem.* **23**, 3808–3818.
- Keene, T. D., Ogilvie, H. R., Hursthouse, M. B. & Price, D. J. (2004). *Eur. J. Inorg. Chem.* pp. 1007–1013.
- Mathoniere, C., Nuttall, C. J., Carling, S. G. & Day, P. (1996). *Inorg. Chem.* **35**, 1201–1206.
- Otwinowski, Z. & Minor, W. (1997). *Methods in Enzymology*, Vol. 276, *Macromolecular Crystallography*, Part A, edited by C. W. Carter Jr & R. M. Sweet, pp. 307–326. New York: Academic Press.
- Price, D. J., Tripp, S., Powell, A. K. & Wood, P. T. (2001). *Chem. Eur. J.* **7**, 200–208.
- Sheldrick, G. M. (1997). *SHELXL97*. University of Göttingen, Germany.
- Sheldrick, G. M. (2003). *SADABS*. Version 1.10. University of Göttingen, Germany.