

Article

Mechanism of Reduced Sintering Temperature of Al₂O₃–ZrO₂ Nanocomposites Obtained by Microwave Hydrothermal Synthesis

Iwona Koltsov ^{1,*}, Julita Smalc-Koziorowska ¹, Marta Przeźniak-Welenc ², Maria Małysa ¹, Giora Kimmel ³, Jessica McGlynn ⁴, Alexey Ganin ⁴ and Swietlana Stelmakh ¹

¹ Institute of High Pressure Physics, Polish Academy of Sciences, Sokolowska 29/37, 01-142 Warsaw, Poland; julita.smalc.koziorowska@unipress.waw.pl (J.S.-K.); malysa.maria@gmail.com (M.M.); svetlana.stelmakh@unipress.waw.pl (S.S.)

² Faculty of Applied Physics and Mathematics, Gdansk University of Technology, Narutowicza 11/12, 80-233 Gdansk, Poland; mprzesniak@mif.pg.gda.pl

³ Department of Nuclear Engineering, Ben-Gurion University of the Negev, Beer Sheva 8410501, Israel; kimmel@exchange.bgu.ac.il

⁴ WestCHEM, School of Chemistry, University of Glasgow, University Avenue, Glasgow G12 8QQ, UK; j.mcglynn.1@research.gla.ac.uk (J.M.); alexey.ganin@glasgow.ac.uk (A.G.)

* Correspondence: iwona.koltsov@unipress.waw.pl; Tel.: +48-22-888-0036

Received: 10 April 2018; Accepted: 14 May 2018; Published: 17 May 2018

Abstract: A novel method to obtain Al₂O₃–ZrO₂ nanocomposites is presented. It consists of the co-precipitation step of boehmite (AlO(OH)) and ZrO₂, followed by microwave hydrothermal treatment at 270 °C and 60 MPa, and by calcination at 600 °C. Using this method, we obtained two nanocomposites: Al₂O₃–20 wt % ZrO₂ and Al₂O₃–40 wt % ZrO₂. Nanocomposites were characterized by Fourier transformed infrared spectroscopy, Raman spectroscopy, X-ray diffraction, and transmission electron microscopy. Sintering behavior and thermal expansion coefficients were investigated during dilatometric tests. The sintering temperatures of the nanocomposites were 1209 °C and 1231 °C, respectively—approximately 100 °C lower than reported for such composites. We attribute the decrease of the sintering temperature to the specific nanostructure obtained using microwave hydrothermal treatment instead of conventional calcination. Microwave hydrothermal treatment resulted in a fine distribution of intermixed highly crystalline nanoparticles of boehmite and zirconia. Such intermixing prevented particle growth, which is a factor reducing sintering temperature. Further, due to reduced grain growth, stability of the θ-Al₂O₃ phase was extended up to 1200 °C, which enhances the sintering process as well. For the Al₂O₃–20 wt % ZrO₂ composition, we observed stability of the zirconia tetragonal phase up to 1400 °C. We associate this stability with the mutual separation of zirconia nanoparticles in the alumina matrix.

Keywords: microwave hydrothermal synthesis; Al₂O₃–ZrO₂ nanocomposites; shrinkage temperature; grain boundaries; isolation effect of t-ZrO₂; phase composition

1. Introduction

Alumina-toughened zirconia (ATZ) and zirconia-toughened alumina (ZTA) are important materials for high-temperature structural [1–3] and medical [4–7] applications due to their excellent strength and toughness, high wear resistance and temperature stability, and the fact that they are both chemically inert. In order to obtain these properties, the tetragonal metastable phase of zirconia (t-ZrO₂) needs to remain stable at room temperature; however, t-ZrO₂ is normally only stable at

temperatures above 1170 °C. One method for ensuring that t-ZrO₂ remains stable at room temperature is to partially stabilize it with an yttria (Y₂O₃) dopant (YSZ) [4–6,8,9].

In general, there are two ways to stabilize t-ZrO₂ particles: the first is by alloying them with other materials while the other is by ensuring that their particle size does not exceed 35 nm. Stabilization of the t-ZrO₂ phase requires certain special synthesis techniques to be used, especially when one desires to have a uniform zirconia particle distribution in an alumina matrix [10,11]. Recent work has shown that synthesizing Al₂O₃ with ZrO₂ nanopowders (up to ~40 wt % ZrO₂) could lead to the partial stabilization of t-ZrO₂ [12].

In ZTA composites, t-ZrO₂ nanoparticles are stable at room temperature; however, under stress, these nanoparticles may undergo a transformation from the tetragonal to the monoclinic phase [8,13,14]. More specifically, if cracks were to propagate through such a ceramic, then any t-ZrO₂ particles in the region of the crack could potentially undergo a martensitic transformation from the tetragonal (t-ZrO₂) to the monoclinic phase (m-ZrO₂); a volume expansion of about 3% would also occur. This would generate compressive stresses in the alumina matrix, preventing the crack from increasing in size and causing the fracture toughness of the ceramic to increase [15,16].

Various chemical methods have so far been used to synthesize Al₂O₃–ZrO₂ and YSZ/Al₂O₃ ceramics, such as the sol-gel method [17], hydrothermal synthesis followed by calcination [18], and the co-precipitation method [19]. Another method, the microwave hydrothermal synthesis method (MHS), has been found to be particularly attractive due to its potential to produce highly crystalline nanoparticles with a narrow particle size distribution [20,21].

Microwave hydrothermal synthesis (MHS) is a method which possesses many advantages in comparison to standard heating methods [20–22]. Firstly, the MHS method is characterized by considerably shorter reaction time. In very short time, the reaction vessel is heated up rapidly and uniformly and the precipitate is heated directly through the energy of microwaves. As a result, heat is generated within the whole volume of the sample and not transported through the reaction vessel walls from an external heat source [22]. Secondly, thanks to uniform heating, the crystallization process in the sample is quick and uniform, resulting in a narrow and nanometric particle size distribution [21–24]. Another advantage is that reaction vessels used in MHS do not introduce contaminants by the contactless heating method. In addition, the low thermal conductivity (0.25 W/(m K)) of Teflon® causes a small temperature gradient between a sample and a vessel which contributes to the uniformity of the product [21]. The biggest advantage of microwave synthesis over other synthesis methods is that it delivers energy directly to the substance without thermal-conductivity-related constraints [22].

Microwave hydrothermal synthesis methods can be used to produce nanomaterials with a variety of morphologies and programmed sizes. Variations in these attributes can significantly affect the properties of final products [25]. Furthermore, using MHS for the production of ZrO₂–Al₂O₃ nanopowders may lead to the isolation of t-ZrO₂ in the alumina matrix in these materials, and thus to the reduction of aggregation.

ZrO₂–Al₂O₃ nanocomposites are often obtained by the sintering of compactified powders [11,26–29]. The microstructure of a ceramic depends upon the structure of the initial materials used for its synthesis, the dopant distribution used, the heating rate, and the sintering mechanism used. For the manufacture of Al₂O₃–ZrO₂ ceramics, it is crucial that a suitable sintering temperature is chosen. One study that illustrates this was conducted by Zhuravlev et al. [30], who showed that the maximum density of Al₂O₃ ceramics with partially stabilized ZrO₂ (3YSZ) was achieved during sintering at 1400–1500 °C. The density of composite decreased and the open porosity of the ceramic materials grew with increasing amount of Al₂O₃. Several studies have manufactured dense ceramics while maintaining a small grain size; most of them used optimized sintering strategies or advanced sintering techniques [11,26,31]. Numerous analyses of the mechanical properties of Al₂O₃–ZrO₂ composite systems have also been reported upon [32–37], and a wide range of results have been presented. These results were influenced by the fabrication routes used, the composition design, and the measurement technique used.

However, there is a lack of data in the literature about the sintering behavior of $\text{Al}_2\text{O}_3\text{-ZrO}_2$ nanocomposites obtained by the method involving co-precipitation and subsequent MHS. Co-precipitation leads to the uniform distribution of components which is very difficult to achieve when mixing the two powders. MHS, meanwhile, leads to the creation of fully crystalline particles (which are not synthesized in the sol-gel process). The sintering of fully crystalline particles may lead to ceramic structures being created than could not be obtained by the sintering of sol-gel-precipitated particles.

The aim of the work was to develop a new method for the manufacturing of $\text{Al}_2\text{O}_3\text{-ZrO}_2$ nanocomposites with stable t- ZrO_2 and with reduced sintering temperature. The present work reports a series of experiments for finely grained $\text{Al}_2\text{O}_3\text{-ZrO}_2$ nanocomposites with 20 and 40 wt % ZrO_2 . Nanocomposites were obtained by co-precipitation and MHS before being thermally treated. We discuss the roles that chemical composition, morphology, and phase composition had in reducing the sintering temperature used for the synthesis of nanocomposites to levels significantly below that found in the literature for $\text{Al}_2\text{O}_3\text{-3YSZ}$ and $\text{Al}_2\text{O}_3\text{-ZrO}_2$.

2. Materials and Methods

The procedure for synthesizing nanopowders containing boehmite ($\text{AlO}(\text{OH})$) with 20 and 40 wt % ZrO_2 is described in detail elsewhere [12]. The reagents used in the process were zirconyl chloride octahydrate ($\text{ZrOCl}_2 \cdot 8\text{H}_2\text{O}$, Sigma-Aldrich ($\geq 99.5\%$)), sodium hydroxide (CHEMPUR, analytically pure), and aluminium nitrate nonahydrate ($\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$, CHEMPUR, analytically pure). Microwave reactions took place in a MAGNUM II ERTEC microwave reactor (2.45 GHz, 600 W). The synthesis of a homogenous mixture of Al_2O_3 and ZrO_2 nanocomposites took place in four steps:

- The first was the co-precipitation of the precursors;
- The second was 20 min of MHS at $t = 270^\circ\text{C}$ and $p = 60$ atm, in order to obtain a crystalline mixture of $\text{AlO}(\text{OH})$ and ZrO_2 ;
- The third was the drying of the precipitates at room temperature. The mixture of nanopowders obtained in step three will be called $\text{AlO}(\text{OH})\text{-ZrO}_2$ or as-synthesized;
- The fourth step was calcination of nanopowder mixture at 600°C for 2 h in order to obtain ZrO_2 with $\gamma\text{-Al}_2\text{O}_3$ originated from $\text{AlO}(\text{OH})$.

Following the above-described four-step procedure, a homogenous mixture of Al_2O_3 and ZrO_2 nanopowders was produced. For the characterization experiments carried out in this work, some of the calcinated powders were also conventionally sintered in air at 1200, 1400 and 1500°C for 1 h.

Samples were prepared for inductively coupled plasma optical emission spectroscopy (ICP-OES, Perkin-Elmer, Optima 8300, Waltham, MA, USA) in a microwave mineralizer (AntonPaar, MW 3000, Graz, Austria) in a Teflon vial using a mixture of acids, namely, HF/HNO_3 and H_2SO_4 . The ICP-OES tests were conducted according to the standard procedure described in EN ISO 11885:2009 [38].

Before and after heating, samples were examined using a Fourier transform infrared (FTIR) spectrometer (Bruker Optics, Tensor 27, Bruker BioSpin GmbH, Rheinstetten, Germany) equipped with a diamond attenuated total reflectance (ATR) accessory. The diamond ATR crystal was soldered onto a ceramic plate; this resulted in the sampling area being chemically inert and mechanically rugged. All of the ATR-FTIR spectra were recorded at room temperature in the $4000\text{-}400\text{ cm}^{-1}$ range. The spectral resolution and accuracy of the measurements were $\pm 4\text{ cm}^{-1}$ and $\pm 1\text{ cm}^{-1}$, respectively.

A Raman scattering spectroscopy (Horiba-Jobin-Yvon, LabRam, HR800, Kyoto, Japan) operated with a $\lambda = 532\text{ nm}$ laser was used to investigate samples annealed at 600 and 1400°C . In order to prevent the samples from degrading, a 10% filter was used. Additionally, an aperture size of $100\text{ }\mu\text{m}$ was used.

X-ray diffraction (XRD) patterns of the nanopowders were collected on a diffractometer (X'Pert PRO, PANalytical, Almelo, Netherlands) equipped with a copper anode ($\text{Cu K}\alpha 1$) and an ultra-fast PIXcel1D detector. The analysis was performed at room temperature in the 2θ range of $10\text{-}100^\circ$ with a step size of 0.03° . All of the diffraction data was analyzed using advanced data processing methods, including Rietveld refinement [39], by the programs DBWS [40] and FullProf [41]; these were used for the structural and quantitative phase analyses, respectively. The peak shape function used in calculation was pseudo-voigt.

The surface morphology was evaluated using a scanning electron microscope (Zeiss, Ultra Plus, Zeiss, Oberkochen, Germany), and the compositions of the nanopowders were estimated semiquantitatively using energy dispersive spectroscopy (EDS) (QUANTAX 400, Bruker, Billerica, MA, USA). For this evaluation, the synthesized materials were compacted to pellets and sintered at 1300 °C for 1 h. Measurements were done as per the ISO 22309:2011 standard [42].

The microstructures of the nanopowders and nanocomposites were investigated using conventional high-resolution (HR) transmission electron microscopy (TEM) and scanning (STEM) techniques with a FEI TECNAI G2 F20 S-TWIN electron microscope (Thermo Fisher Scientific, Waltham, MA, USA).

Helium density measurements were carried out using a helium pycnometer (AccuPyc II 1340, FoamPyc V1.06, Micromeritics, Norcross, GA, USA). The measurements were carried out in accordance with the ISO 12154:2014 standard [43] at temperatures of 25 ± 2 °C.

The specific surface area (SSA) of the nanopowders was determined in accordance with ISO 9277:2010 [44]; more specifically, a surface analyzer (Gemini 2360, V 2.01, Norcross, GA, USA) that used the nitrogen adsorption method was used, and this method was based on the linear form of the Brunauer–Emmett–Teller (BET) isotherm equation. The detailed experimental procedure and the determination of particle size using the BET method (SSA_{BET}) is described elsewhere [12].


In order to calculate the crystallite diameter and size distribution, equations dedicated to spherical crystallites in the Nanopowder XRD Processor Demo (Pielaszek Research) web application were used. The website provides an online tool in which diffraction files can be directly uploaded [45]; the files are then processed on a server and the particle size distribution for the XRD peaks is extracted.

The nanopowders calcinated at 600 °C were compacted at room temperature in a stainless steel mold under 250 bar. Dilatometric experiments were also carried out; for these, cylindrical specimens with 5 mm diameters and ca. 5 mm heights were prepared. The shrinkage behavior of bulk samples and their relative changes in length were examined using a Netzsch DIL 402 PC/4 dilatometer in an argon ambient atmosphere between 40 and 1500 °C at a constant heating and cooling rate of 2 °C min^{-1} . The densification rate was obtained by differentiating the measured linear shrinkage data. The temperature at which a change in the slope of the dilatometric relative length curve occurred was taken as being the phase transition temperature.

3. Results

Figure 1 shows the FTIR spectra for (a), (b) as-synthesized AlO(OH)–ZrO₂ nanopowders, (c) nanopowders after calcination at 600 °C, and (d) after annealing at 1400 °C. Pure ZrO₂, boehmite (AlO(OH)), and Al₂O₃ were added as references. The bands observed for the as-synthesized samples were identified; they are listed in Table 1 [10,36,37,46–52].

Figure 2 shows Raman spectra for Al₂O₃–ZrO₂ nanocomposites calcinated at 600 °C and for pellets sintered at 1400 °C. The relevant peaks reported in the literature for t-ZrO₂, m-ZrO₂, and Al₂O₃ are listed in Table 2.

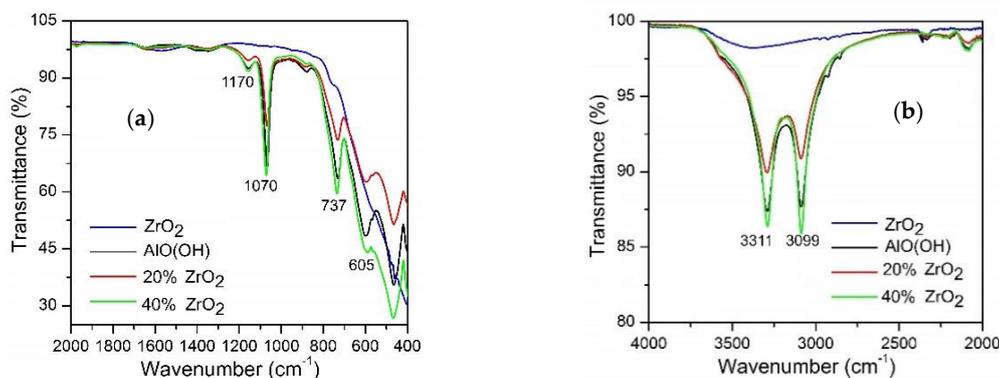

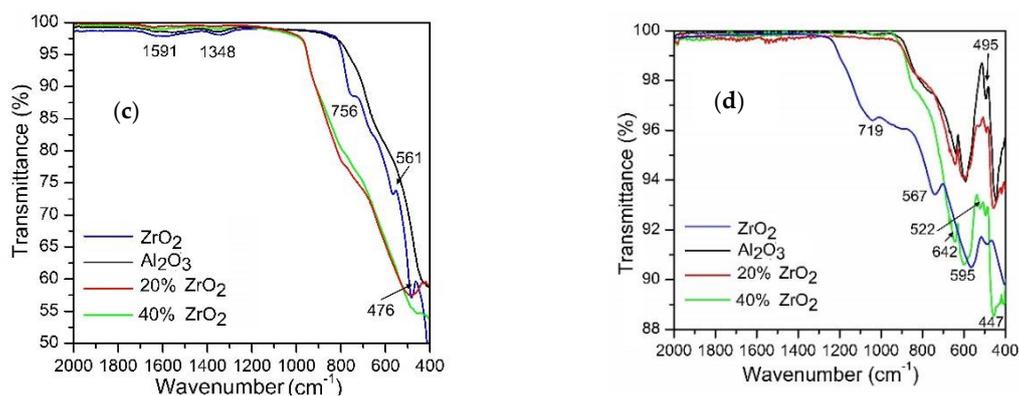


Figure 1. FTIR spectra for Al_2O_3 –(20,40 wt %) ZrO_2 in as-synthesized form (a,b), calcined at 600 °C (c), and after annealing at 1400 °C (d).

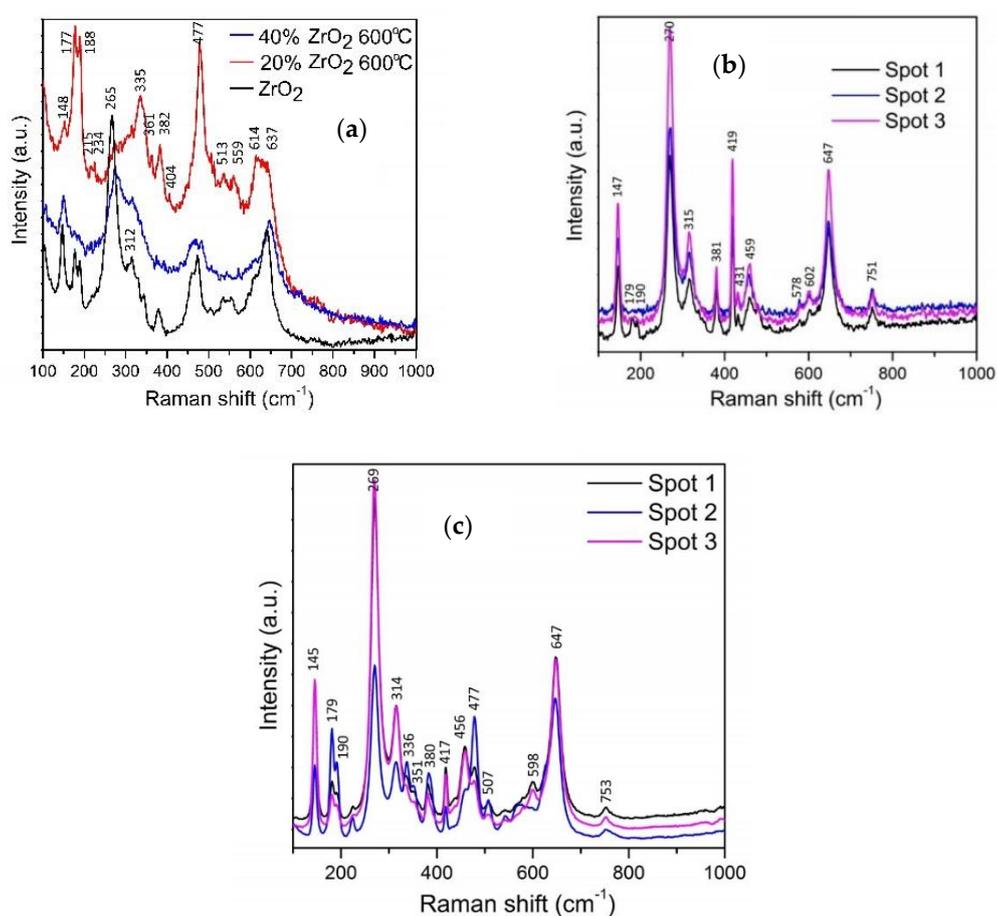


Figure 2. Raman spectra for (a) Al_2O_3 –(20,40 wt %) ZrO_2 after annealing at 600 °C, (b) Al_2O_3 –20 wt % ZrO_2 after annealing at 1400 °C, and (c) Al_2O_3 –40 wt % ZrO_2 after annealing at 1400 °C.

Table 1. Characterization of FTIR-ATR bands in Al₂O₃–(20,40 wt %) ZrO₂ samples.

ZrO ₂ Bands in As-Synthesized Samples (cm ⁻¹)	Literature	AlO(OH) Bands in As-Synthesized Samples (cm ⁻¹)	Literature
		472, 605	Bands between 780 and 500 cm ⁻¹ can be assigned to the vibration mode of AlO ₆ [36]
		737	Al–O–Al framework [37]
		900	Al–O band stretching vibration of boehmite [10]
		1070, 1170	(HO)–Al=O asymmetric stretching and the O–H bending, respectively [46]
1338	Bending vibration of Zr–OH groups [37], and it might be t-ZrO ₂ [48]	1170	Al–O–H vibrations [46]
1566	t-ZrO ₂ [48]	1668	O–H bending mode [37]
3357	Stretching vibration of hydroxyl group and the interlayer water molecules [40]	3099, 3311	Asymmetric and symmetric O–H stretching vibrations from (O)Al–OH [37]
ZrO ₂ Bands in Annealed Samples (cm ⁻¹)	Literature	Al ₂ O ₃ Bands in Annealed Samples (cm ⁻¹)	Literature
440	symmetric Zr–O–Zr stretching mode related with t-ZrO ₂ phase [46] It might be ν(Zr–O) band from t-ZrO ₂ [51]	447	Al–O stretching mode in α-Al ₂ O ₃ [47]
484	t-ZrO ₂ [52], stretching vibrations of Zr–O in ZrO ₂	495	α-Al ₂ O ₃ [47]
567 719	Zr–O stretching vibrations [50]	595	Al–O stretching mode in octahedral structure [50]
		642	asymmetric Zr–O–Zr stretching mode from the m-ZrO ₂ phase [49]

Table 2. Raman spectral data for Al₂O₃–(40,20 wt %) ZrO₂ after annealing at 600 °C and 1400 °C [45,52–55].

Al ₂ O ₃ –(20,40 wt %)ZrO ₂ after Annealing at 600 °C	Wavenumbers (cm ⁻¹)	Literature	Al ₂ O ₃ –(20,40 wt %)ZrO ₂ after Annealing at 1400 °C	Wavenumbers (cm ⁻¹)	Literature
			Al ₂ O ₃ –(20 wt %) ZrO ₂ after annealing at 1400 °C		
t-ZrO ₂	148, 265, 312	[49]	t-ZrO ₂	147, 270, 315, 459	[49]
m-ZrO ₂	177, 188, 215, 355, 382, 477, 513, 559, 637	[49]	m-ZrO ₂	179, 190, 381, 419, 578, 647	[49]
γ-Al ₂ O ₃	234, 404	[52,53]	α-Al ₂ O ₃	381, 419, 431,578,647, 751	[52–55]
			Al ₂ O ₃ –(40 wt %) ZrO ₂ after annealing at 1400 °C		
			t-ZrO ₂	145,269, 314, 456	[49]
			m-ZrO ₂	179, 190, 336, 351, 380, 417, 477, 507, 598, 647	[49]
			α-Al ₂ O ₃	380, 417, 647, 753	[52–55]

The morphology of as-synthesized AlO(OH)–ZrO₂ nanopowders is presented in Figure 3. There is very little difference between samples in terms of shape and particle size. In addition, Figure 4 shows TEM and SEM images of morphology and structure for nanocomposites obtained after annealing at 1400 °C.

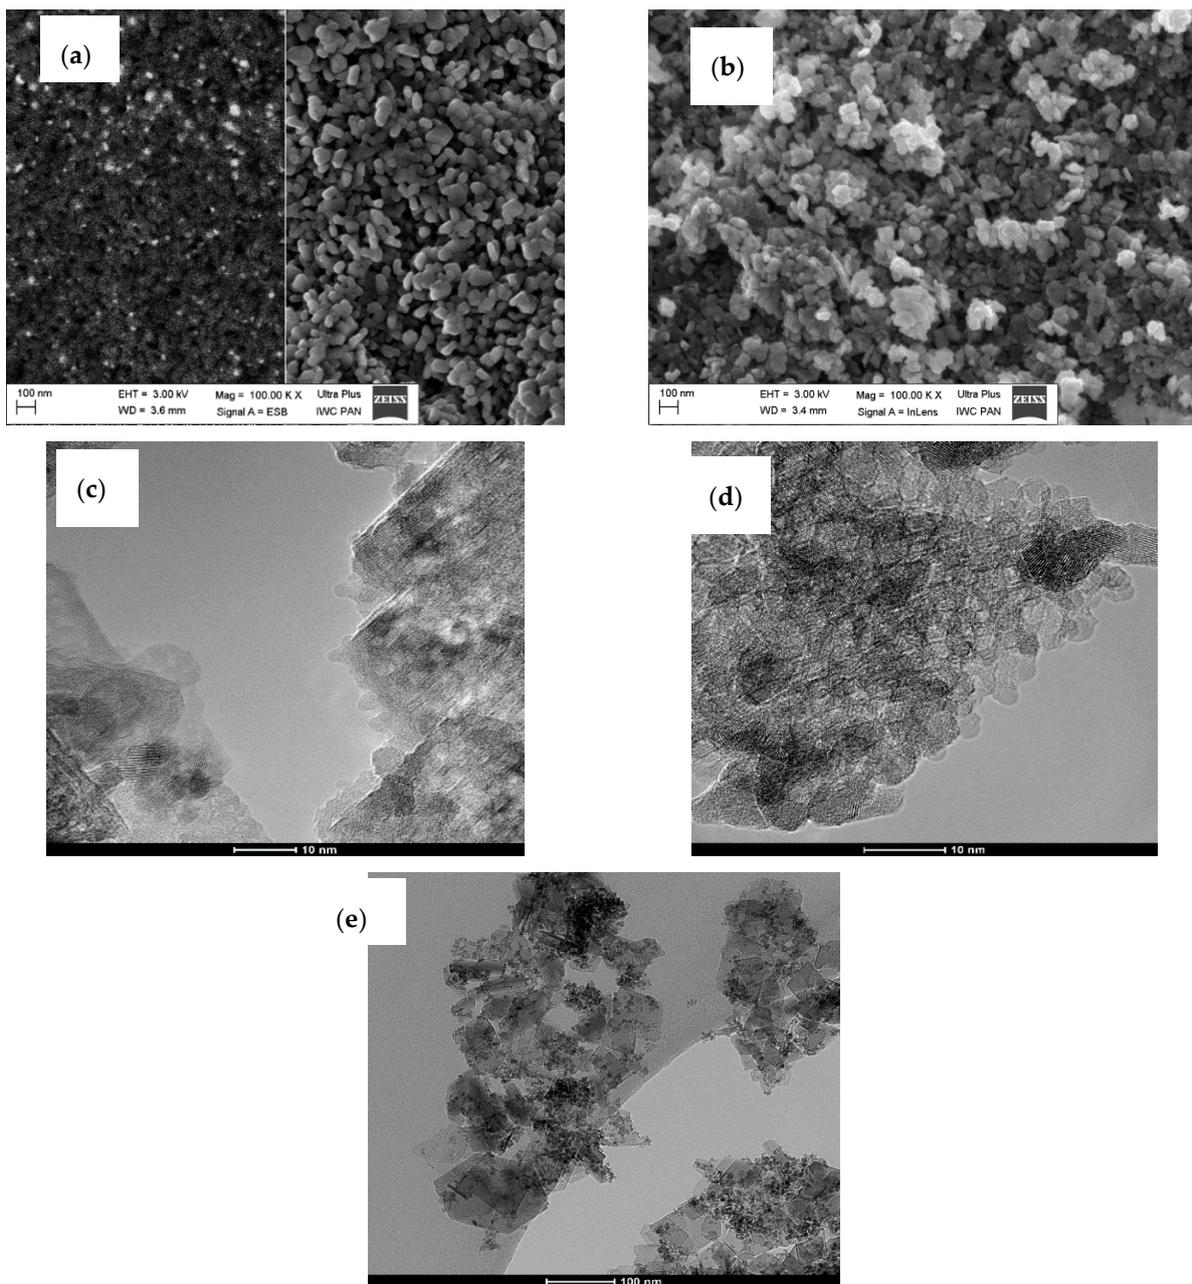
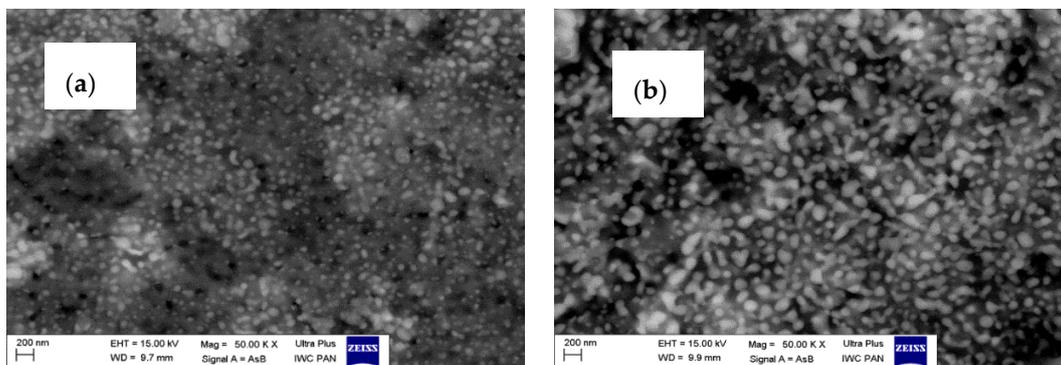


Figure 3. SEM and TEM images for Al₂O₃-20 wt % ZrO₂ after synthesis (a,c), and Al₂O₃ with 40 wt % ZrO₂ after synthesis (b,d,e).



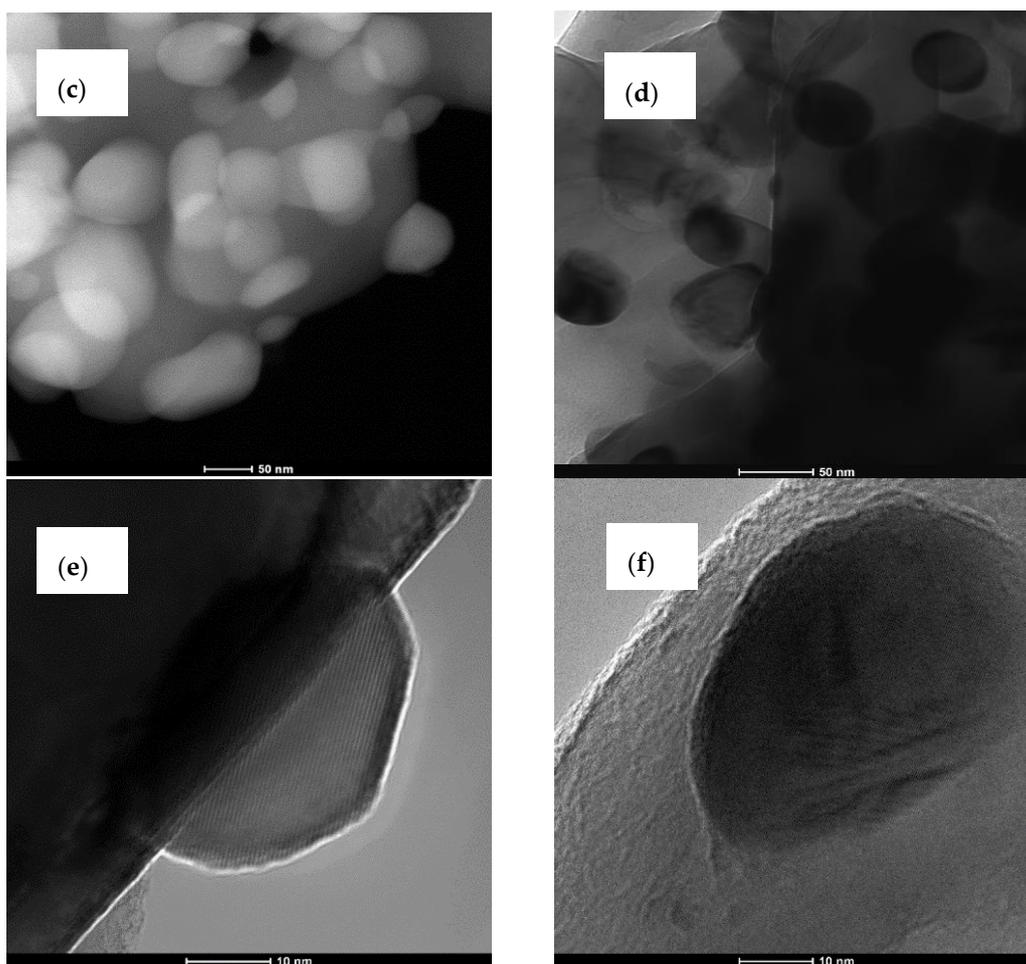


Figure 4. SEM and TEM images for Al_2O_3 -20 wt % ZrO_2 after annealing at 1400 °C (a,c,e), and Al_2O_3 -40 wt % ZrO_2 after annealing at 1400 °C (b,d,f).

Particle size distributions for ZrO_2 phases (both t- ZrO_2 and m- ZrO_2) are shown in Figure 5. Calculation was prepared based on XRD experiments.

The results for SSA_{BET} and density of nanopowders after calcination at 600 °C and 1400 °C are shown in Table 3. For both compositions there is visible difference in SSA_{BET} values after annealing at 600 °C: 177.2 for Al_2O_3 -20 wt % ZrO_2 and 95.9 m^2/g for Al_2O_3 -40 wt % ZrO_2 . The density values are comparable (3.5 g/cm^3 for Al_2O_3 -20 wt % ZrO_2 and 3.8 g/cm^3 for Al_2O_3 -40 wt % ZrO_2).

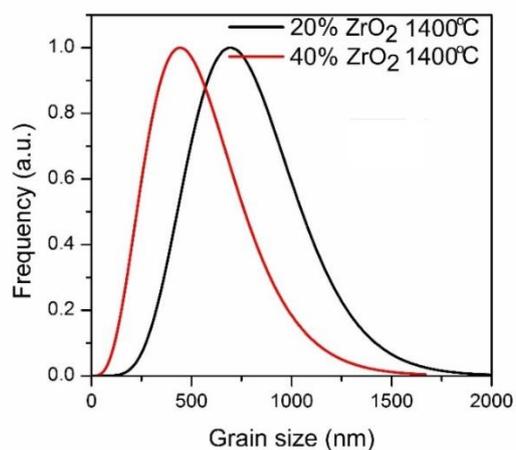
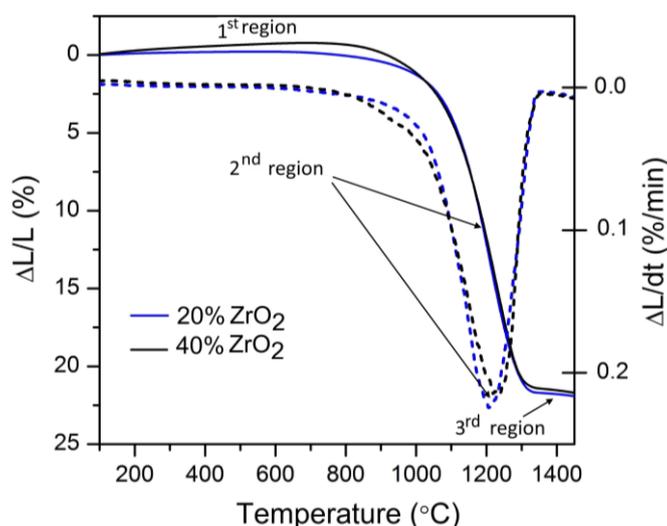


Figure 5. Particle size distribution for Al_2O_3 -(20,40 wt %) ZrO_2 nanocomposites after annealing at 1400 °C.

Table 3. Comparison of specific surface area (SSA_{BET}), helium density, and particle size for Al_2O_3 –(20,40 wt %) ZrO_2 nanocomposites annealed at 600 °C and 1400 °C.

Composition (wt %)	Thermal Treatment	Specific Surface Area SSA_{BET} (m^2/g)	Helium Density (g/cm^3)	Densification (%)
Al_2O_3 –20% ZrO_2	600 °C	177.2097 ± 0.6228	3.5442 ± 0.0062	84
	1400 °C	3.3659 ± 0.0085	4.2073 ± 0.0087	
Al_2O_3 –40% ZrO_2	600 °C	95.9208 ± 0.4215	3.8257 ± 0.0455	90
	1400 °C	0.5900 ± 0.0042	4.2260 ± 0.0133	

Figure 6 shows dilatometry curves for Al_2O_3 –20 wt % ZrO_2 and Al_2O_3 –40 wt % ZrO_2 with three distinguished regions characteristic of the sintering process.

**Figure 6.** Dilatometric curves for Al_2O_3 –(20,40 wt %) ZrO_2 nanocomposites (solid lines), where dotted lines represent first derivative.

In Table 4 we show results of chemical and phase composition of Al_2O_3 –(20,40 wt %) ZrO_2 nanocomposites annealed in the 600–1400 °C temperature range. These results were obtained from ICP-OES, EDS, and Rietveld refinement analysis.

Table 4. Chemical and phase composition of Al_2O_3 –(20,40 wt %) ZrO_2 nanocomposites annealed in the 600–1400 °C temperature range.

Composition (wt %)	EDS (wt % of ZrO_2)	ICP-OES (wt % of ZrO_2)	Phase Composition Obtained from Rietveld Refinement for Samples after Annealing at Different Temperatures (wt %)		
			600 °C	1200 °C	1400 °C
Al_2O_3 –20% ZrO_2	20.14 ± 1.37	21 ± 1.09	83.3 γ – Al_2O_3	82.3 θ – Al_2O_3	80.5 α – Al_2O_3
			12.9 t – ZrO_2	14.5 t – ZrO_2	12.6 t – ZrO_2
			3.8 m – ZrO_2	3.2 m – ZrO_2	6.8 m – ZrO_2
Al_2O_3 –40% ZrO_2	38.47 ± 2.61	40 ± 0.81	67.4 γ – Al_2O_3	61.3 θ – Al_2O_3	59.4 α – Al_2O_3
			25.9 t – ZrO_2	13.8 t – ZrO_2	8.0 t – ZrO_2
			6.7 m – ZrO_2	24.9 m – ZrO_2	32.6 m – ZrO_2

Rietveld refinements for Al_2O_3 –(20,40 wt %) ZrO_2 nanocomposites are presented in Figure 7. Refinement was performed for nanocomposites after annealing at 600 °C, 1200 °C and 1400 °C. Peak positions coming from analyzed phases are marked on the figures. Atom positions in analyzed phases as well as cell parameters are presented in Tables 5 and 6.

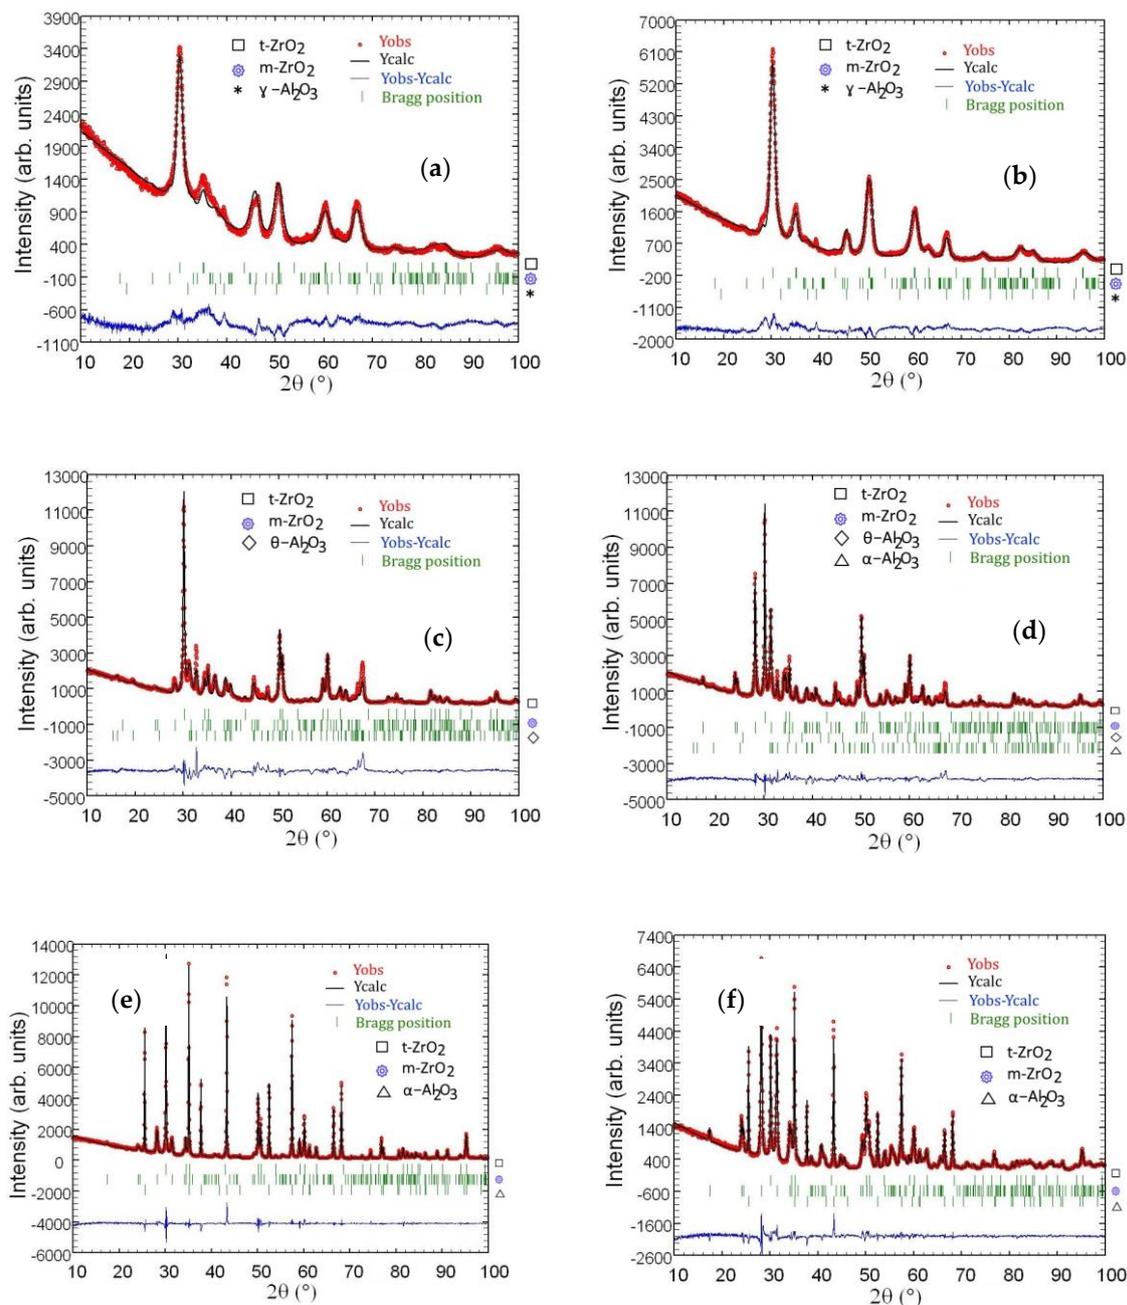


Figure 7. Rietveld refinement for Al_2O_3 -20 wt % ZrO_2 after annealing at 600 °C for 2 h (a), 1200 °C (c), 1400 °C (e), and Al_2O_3 -40 wt % of ZrO_2 after annealing at 600 °C for 2 h (b), 1200 °C (d), 1400 °C (f).

Table 5. Atom position in θ - Al_2O_3 , α - Al_2O_3 , m- ZrO_2 , and t- ZrO_2 based on Rietveld refinement.

Phase: θ - Al_2O_3 , C 2/m				Phase: m- ZrO_2 , P 21/c			
Atom Position	x	y	z	Atom Position	x	y	z
Al1:Al ³⁺	0.10130	0.00000	0.79440	Zr:Zr ⁴⁺	0.27605	0.03987	0.20927
Al2:Al ³⁺	0.35230	0.00000	0.68740	O1:O ²⁻	0.06633	0.33052	0.34468
O1:O ²⁻	0.16270	0.00000	0.12280	O2:O ²⁻	0.45232	0.75875	0.47537
O2:O ²⁻	0.48950	0.00000	0.26130				
O3:O ²⁻	0.82990	0.00000	0.43860				
Phase: α - Al_2O_3 , 167				Phase: t- ZrO_2 , P 42/nmc			
Atom Position	x	y	z	Atom Position	x	y	z
Al:Al ³⁺	0.00000	0.00000	0.35230	Zr:Zr ⁴⁺	0.75000	0.25000	0.75000
O:O ²⁻	0.30640	0.00000	0.25000	O:O ²⁻	0.25000	0.25000	0.55000

Table 6. Cell parameters of θ -Al₂O₃, α -Al₂O₃, m-ZrO₂, and t-ZrO₂ phases calculated in Rietveld refinement for Al₂O₃-20 wt % ZrO₂ and Al₂O₃-40 wt % ZrO₂ nanocomposites annealed at 1200 °C and 1400 °C.


Unit cell dimensions in Al ₂ O ₃ -20 wt %ZrO ₂							
T = 1200 °C				T = 1400 °C			
Phase:		t-ZrO ₂		Phase:		t-ZrO ₂	
a (Å)	b (Å)	c (Å)	α, β, γ (°)	a (Å)	b (Å)	c (Å)	α, β, γ (°)
3.597020	3.597020	5.191563	$\alpha = \beta = \gamma$ 90.0000	3.598789	3.598789	5.200136	$\alpha = \beta = \gamma$ 90.0000
Phase:		m-ZrO ₂		Phase:		m-ZrO ₂	
5.093851	5.141055	5.313514	$\alpha = \gamma; \beta$ 90.0000; 100.5483	5.149243	5.186935	5.318353	$\alpha = \gamma; \beta$ 90.0000; 99.0302
Phase:		θ -Al ₂ O ₃		Phase:		α -Al ₂ O ₃	
11.802021	2.911568	5.622274	$\alpha = \gamma; \beta$ 90.0000; 104.0478	4.760565	4.760565	12.996780	$\alpha = \beta; \gamma$ 90.0000; 120.0000
Unit cell dimensions in Al ₂ O ₃ -40 wt %ZrO ₂							
T = 1200 °C				T = 1400 °C			
Phase:		t-ZrO ₂		Phase:		t-ZrO ₂	
a (Å)	b (Å)	c (Å)	α, β, γ (°)	a (Å)	b (Å)	c (Å)	α, β, γ (°)
3.597343	3.597343	5.194126	$\alpha = \beta = \gamma$ 90.0000	3.599882	3.599882	5.200407	$\alpha = \beta = \gamma$ 90.0000
Phase:		m-ZrO ₂		Phase:		m-ZrO ₂	
5.146611	5.188430	5.310700	$\alpha = \gamma; \beta$ 90.0000; 98.9165	5.152256	5.190232	5.315270	$\alpha = \gamma; \beta$ 90.0000; 99.0657
Phase:		θ -Al ₂ O ₃		Phase:		α -Al ₂ O ₃	
11.795719	2.911480	5.620936	$\alpha = \gamma; \beta$ 90.0000; 104.0352	4.762267	4.762267	12.999507	$\alpha = \gamma; \beta$ 90.0000; 120.0000

The thermal parameters obtained from dilatometric experiments (including sintering temperature calculated using maximum shrinkage rate) are shown in Table 7. The thermal expansion coefficients were obtained by fitting the relative elongation as a function of temperature with linear functions (Figure 8).

Table 7. Thermal properties for Al₂O₃-(20,40 wt %) ZrO₂ nanocomposites obtained from dilatometry experiments.

Composition (wt %)	Sintering Temperature (°C)	Thermal Expansion Coefficient ¹ (10 ⁻⁶ K ⁻¹)/Structure		Transition Temperature (°C)
		t-ZrO ₂	m-ZrO ₂	
Al ₂ O ₃ -20% ZrO ₂	1209	10.29	N/A	N/A
Al ₂ O ₃ -40% ZrO ₂	1231	8,99	13,84	1153

¹ Thermal expansion coefficients with corresponding transition temperatures obtained for nanocomposites sintered at 1500 °C.

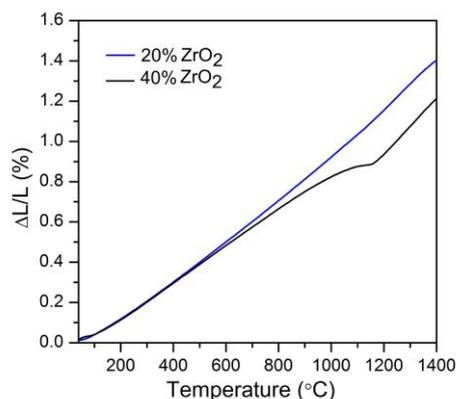**Figure 8.** Shrinkage behavior of Al₂O₃-(20,40 wt %) ZrO₂ nanocomposites.

4. Discussion

FTIR spectra show that there were signals associated with Al–O–H; these bands are characterized by bands in the OH– and water regions at 3311 and 3309 cm^{-1} , respectively, in Figure 1a as well as by bands originating from Al–O in Figure 1b. In the figure, it can be seen that for Al_2O_3 – ZrO_2 (20 and 40 wt %) which are calcinated at 600 °C (Figure 1b), the only well-resolved peak that can be associated with ZrO_2 is that of a broad shoulder that has a maximum at 476 cm^{-1} , which can be assigned to t- ZrO_2 . Following calcination at 600 °C, alumina exists in the form γ - Al_2O_3 ; this is due to a boehmite transformation. Following annealing conducted at 1400 °C, the materials can be characterized by bands originating from Al_2O_3 .

Raman results indicate that all compositions calcinated at 600 °C contained both monoclinic and tetragonal zirconia phases. The amount of m- ZrO_2 is significantly lower for Al_2O_3 –40 wt % ZrO_2 compared to Al_2O_3 –20 wt % ZrO_2 samples (Figure 2a). Furthermore, the Al_2O_3 –40 wt % ZrO_2 composite contains a significantly higher amount of t- ZrO_2 than a pure ZrO_2 sample (e.g., without any addition of Al_2O_3). These observations are in agreement with XRD results described in further paragraphs.

Annealing at 1400 °C of the Al_2O_3 –20 wt % ZrO_2 composition demonstrates that the t- ZrO_2 phase dominates over the monoclinic phase and that the sample is homogeneous (Figure 2c). On the other hand, the composition of Al_2O_3 –40 wt % ZrO_2 shows that ZrO_2 particles are mostly in the monoclinic phase (Figure 2c). Further analysis of the sample at several locations revealed that the sample is not homogeneous with some parts containing a considerable amount of t- ZrO_2 . It is possible to draw a conclusion that a higher content of ZrO_2 leads to greater presence of m- ZrO_2 . Two pronounced peaks at 177 and 188 cm^{-1} indicate that Al_2O_3 has a stabilizing effect on t- ZrO_2 in the case of the Al_2O_3 –20 wt % ZrO_2 composition.

Composites present two types of morphologies: boehmite thin flakes (with particle size ~160 nm), and spherical zirconia particles (with particle size ~3 nm) (Figure 3). Boehmite flakes have rough dimpled surfaces, and the ZrO_2 particles are attached to boehmite flakes. The mean particle size for the Al_2O_3 –20 wt % ZrO_2 sample is visibly smaller than that for the Al_2O_3 –40 wt % ZrO_2 . Both phases— ZrO_2 and boehmite—are uniformly distributed on the SEM and TEM images. Annealing at 1400 °C leads to a visible increase in the ZrO_2 particle size (Figure 4). In addition, ZrO_2 particles (spherical, dark particles) for both composition are isolated in the Al_2O_3 matrix and they are prevented from further growing (Figure 4c,d).

On the other hand, the results of the particle size distributions for ZrO_2 phases (both t- ZrO_2 and m- ZrO_2) presented in Figure 5 show differences between compositions. The mean alumina particle size after sintering at 1400 °C was 480 nm for Al_2O_3 –40 wt % ZrO_2 , and 750 nm for Al_2O_3 –20 wt % ZrO_2 , while the average size of the t- ZrO_2 grains based on TEM observations was 30 nm for both compositions. From TEM images it is also possible to infer that a and c lattice spacings are different in these grains, which confirms that their structure is tetragonal (Figure 4e).

As expected, the specific surface area (SSA_{BET}) and density of the samples were affected by annealing at 600 °C and 1400 °C. The specific surface area for both compositions after annealing at 1400 °C was strikingly different compared to the values obtained after only annealing at 600 °C.

The nanoparticles' size, size distribution, and morphology influence phase transformations in the alumina and zirconia composites. Furthermore, the phase transformation of Al_2O_3 influences the densification process. In the following paragraph, we will therefore discuss the sintering behavior of Al_2O_3 – ZrO_2 nanocomposites in relation to the phase composition.

Dilatometry results for Al_2O_3 –20 wt % ZrO_2 and Al_2O_3 –40 wt % ZrO_2 are presented in Figure 6. Other thermal properties of nanocomposites were previously reported in [56]. Three distinctive regions in dilatometry curves can be found:

- The first (1) refers to the temperature range before the nanocomposite will shrink (before onset temperature— T_{on}). This is the rearrangement region [57] which is visible from RT up to 1100 °C for Al_2O_3 –20 wt % ZrO_2 , and up to 1150 °C for Al_2O_3 –40 wt % ZrO_2 . Both of these values are approximately 100 °C lower than results published recently for a similar system by Scoton et al. [57].

- The second (2) step belongs to the shrinkage process, where the maximum shrinkage rates are found at 1208 °C for Al₂O₃–20 wt % ZrO₂ and 1231 °C for Al₂O₃–40 wt % ZrO₂. Both of these temperatures are also from 100 to 200 °C lower compared to relevant literature [57,58].
- The third (3) step distinguished on the dilatometry curves belongs to the end of the sintering process. The end of the sintering process for both compositions appears at approximately 1300 °C, and is associated with a 22% change of length.

It is important to analyze in detail the phase transformations for the ZrO₂ nanoparticles in the temperature range from 1200 °C to 1400 °C, since nanoparticles sinter rapidly in this temperature region. The results of phase analysis for Al₂O₃–20 wt % ZrO₂ and Al₂O₃–40 wt % ZrO₂ nanopowders as a function of annealing temperature are shown in Figure 7. The phase content of as-synthesized powders was described before [12] and it is composed of fully crystalline boehmite, *t*-ZrO₂, and *m*-ZrO₂. Annealing at 600 °C leads to an AlO(OH)→*γ*-Al₂O₃ transformation. Subsequent annealing of Al₂O₃–20 wt % ZrO₂ and Al₂O₃–40 wt % ZrO₂ at 1200, 1400 and 1500 °C causes the following alumina transformation: *γ*-Al₂O₃→*θ*-Al₂O₃→*α*-Al₂O₃.

It is known that the specific temperatures for alumina transitions depend on the dopant concentration and alumina mean particle size [59]. In particular, the additives that reduce alumina particle growth during sintering and reduce nucleation sites *α*-Al₂O₃ (for example, ZrO₂) [59] strongly influence phase transition temperatures. The second step of alumina nanoparticle transformation (*θ*-Al₂O₃→*α*-Al₂O₃) in nanocomposites is critical to understanding the sintering. For this reason, it is important to determine the temperature regions of stability of the *θ*-Al₂O₃ (theta alumina) phase. Sintering of nanosized Al₂O₃ powders accompanied by grain growth is explained by polymorphic phase transformations [60].

The effects of phase transformation on various Al₂O₃–ZrO₂ composites sintering was already discussed in the literature [10,30,59–62]. For example, Chen et al. [10] found that shrinkage of Al₂O₃–ZrO₂ composites is related to the *θ*→*α*-Al₂O₃ phase transformation taking place in the second step of sintering. During this stage, the coalescence of crystallites and necking were developed, which retarded densification as well as shrinkage. According to the authors [10], the final densification temperature is affected by the microstructure after the *θ*→*α*-Al₂O₃ phase transformation. The authors [10] found that the phase composition of the composite at various annealing temperatures depends on the aging time of the precipitated mixture obtained in the sol-gel process prior to sintering. They reported [10] that the phase transformation of *θ*-Al₂O₃ into *α*-Al₂O₃ can be shifted to temperatures higher than 1300 °C due to aging. Such phase transformation appears to be thanks to the transformation of nano-sized Al₂O₃ powder, and is connected to nucleation and growth processes. It was found that the shorter the aging time, the stronger the interaction between ZrO₂ and Al₂O₃ particles [10]. Additionally, precipitated ZrO₂ particles can prevent Al₂O₃ particles from contact which suppresses coalescence and delays *θ*→*α* phase transformation.

Lamouri et al. [59], who discussed transition of alumina phases and their influence on densification process, found that densification of alumina takes place due to nucleation and grain growth mechanisms. This process is influenced by grain size, starting nanoparticle morphology, dynamics of *θ*→*α* phase transformation in Al₂O₃, and the heating rate of the sintering process. The slow heating rate of the sintering process reduces the temperature of *α*-Al₂O₃ formation which is characterized by high activation energy [59].

In our case, *θ*-Al₂O₃ was observed in both materials even after annealing at temperatures higher than 1200 °C. According to recent publications [60–62], any grain growth process would lead to transformation of theta to alpha phase (*α*-Al₂O₃). In fact, Lamouri et al. [59] found that *θ*→*α*-Al₂O₃ phase transformation can happen only after *θ*-Al₂O₃ coarsens to a critical size (~20 nm). Such coarsening is underpinned by the Ostwald ripening process. The Ostwald ripening rate is determined by the probability of contact between two *θ*-Al₂O₃ particles and the material diffusion process. The precipitated zirconia particles can prevent *θ*-Al₂O₃ particles from coming into contact, thus suppressing the coalescence of *θ*-Al₂O₃ particles which in turn delays the *θ*→*α*-Al₂O₃ phase transformation. Such suppression of coalescence can be readily achieved in samples made by co-precipitation and quick crystallization in a microwave synthesis reactor.

Thus, above 1000 °C as a result of grain growth, only α -Al₂O₃ should be observed. It might be assumed that this process has not taken place during the present study because the addition of ZrO₂ nanoparticles slows down the alumina particle growth. Rietveld refinement analysis of particle size shows that both compositions after annealing at 1400 °C are characterized by 30–80 nm t-ZrO₂ and 50–200 nm m-ZrO₂, while alumina particles are approximately 200 nm in diameter in both cases. In addition, ZrO₂ nanoparticles remain within the alumina matrix grains as well as at the grain boundaries. The smaller ZrO₂ particles seem to be entrapped within the alumina grains and they prevent alumina particles from growing (Figures 4 and 5).

Equally, the nanoparticles' morphology may also influence the transition temperatures between alumina phases. Levin et al. [60] studied phase transformation during annealing of boehmite and showed that the morphology of the starting materials has an influence on the $\theta \rightarrow \alpha$ -Al₂O₃ phase transformation. Lee et al. [61] showed that the platelet γ -Al₂O₃ did not transform to α -Al₂O₃, even after 1100 °C calcination. In our study, the calcination platelet morphology of boehmite was obtained, and no θ to α -Al₂O₃ transformation was observed up to 1200 °C. Our results are in agreement with [61].

An analysis of results presented in Table 4 shows an agreement between nominal (predicted based on the composition of the precursors) and measured weight % of ZrO₂ in all materials. The differences of ZrO₂ wt % values measured by EDS and ICP-OES methods and by using Rietveld refinement are relatively minor. Our results show that the amount of t-ZrO₂ phase in the case of Al₂O₃–20 wt % ZrO₂ composite varies between 12.7 and 15.9 wt % in the whole temperature range. In the Al₂O₃–40 wt % ZrO₂, t-ZrO₂ varies between 8 and 25 wt % (Table 4). For the Al₂O₃–20 wt % ZrO₂ composite, it was observed that amount of the t-ZrO₂ phase was constant (within the experimental error) for the whole temperature range investigated (from 600 °C to 1400 °C). The weight ratio of t-ZrO₂ to m-ZrO₂ was 3.3:1. Only at the 1400 °C temperature was a decrease of t-ZrO₂/m-ZrO₂ observed. It is interesting to note that the t-ZrO₂/m-ZrO₂ ratio after sintering up to 1200 °C was very close to the one observed for the composites of Al₂O₃–3 mol %YSZ presented in [30].

As far as the Al₂O₃–40 wt % ZrO₂ material is concerned, a different behavior was observed in comparison to the Al₂O₃–20 wt % ZrO₂. The t-ZrO₂ phase was dominant only after 600 °C annealing. Further annealing causes a systematic increase of the m-ZrO₂ phase content. This confirms that Al₂O₃–40 wt % ZrO₂ has lower thermal stability, and isolation of t-ZrO₂ in the Al₂O₃ matrix is weaker.

It was found that thermal expansion coefficients for Al₂O₃–40 wt % ZrO₂ vary due to phase transition. Contrary to the Al₂O₃–40 wt % ZrO₂ composition, Al₂O₃–20 wt % ZrO₂ is characterized by only one value of thermal expansion coefficient. The thermal expansion coefficient for Al₂O₃–20 wt % ZrO₂ is $10.29 \times 10^{-6} \text{ K}^{-1}$, while those for Al₂O₃–40 wt % ZrO₂ are 8.99 and $13.84 \times 10^{-6} \text{ K}^{-1}$ (Table 7). This experiment confirms that Al₂O₃–20 wt % ZrO₂ nanocomposite is not characterized by martensitic transformation (t \leftrightarrow m ZrO₂), which is beneficial for mechanical properties. For Al₂O₃–20 wt % ZrO₂ it was found that the t-ZrO₂ phase was stable up to 1400 °C, which is also attributed to nanoparticle separation.

5. Conclusions

In this paper, we showed a new method for the manufacturing of Al₂O₃–ZrO₂ nanocomposites with reduced sintering temperature. The sintering temperatures were found to be 1209 °C for Al₂O₃–20 wt % ZrO₂ and 1231 °C for Al₂O₃–40 wt % ZrO₂ nanocomposites. These temperatures were approximately 100 °C lower than previously reported for similar compositions. In the above nanostructures, the θ -Al₂O₃ nanoparticles are surrounded by small zirconia nanoparticles, which prevent their growth and stabilize the θ -phase up to 1200 °C. The reason for the decrease of the sintering temperature is related to:

- Uniform distribution of zirconia nanoparticles within the alumina matrix;
- Maintaining up to relatively high temperature a grain size in the nano range. As it is known, the driving force for sintering nanomaterials is higher than that for microcrystals;
- θ -Al₂O₃ stability was extended up to 1200 °C, with enhancement of that phase's sintering.

For the Al₂O₃–20 wt % ZrO₂ composition, we observed stability of the zirconia tetragonal phase up to 1400 °C. We associate such stability with the mutual separation of zirconia nanoparticles in the alumina matrix. A different behavior was observed for Al₂O₃–40 wt % ZrO₂. The t-ZrO₂ phase was dominant only after 600 °C annealing. Further annealing causes a systematic increase of the m-ZrO₂ phase content. This confirms that Al₂O₃–40 wt % ZrO₂ has lower thermal stability, and isolation of t-ZrO₂ in the Al₂O₃ matrix is weaker.

Author Contributions: I.K. conceived and designed experiments, wrote the paper, synthesized materials, and performed SEM and FTIR tests/analysis of results; J.S.-K. performed TEM imaging; M.P.-W. conducted dilatometry experiments; M.M. prepared pellets for sintering and ran annealing processes; G.K. carried out Rietveld refinement analysis; J.M. and A.G. performed Raman spectroscopy experiments and analysed the data, S.S. performed XRD/particle size distribution analysis. This publication is part of Iwona Koltsov's habilitation thesis. All authors contributed to discussion and editing of the manuscript.

Funding: This research was funded by Polish National Science Centre grant number: UMO-2013/11/D/ST8/03429- "Sonata 6". The research subject was partly carried out with the use of equipment funded by the project CePT, reference: POIG.02.02.00-14-024/08, financed by the European Regional Development Fund within the Operational Programme "Innovative Economy" for 2007–2013.

Acknowledgments: Authors are indebted to Jan Mizeracki for help in SEM analysis, and to Denis Koltsov, Witold Łojkowski, and Jacek Wojnarowicz for scientific discussion.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Chandradass, J.; Kim, M.H.; Bae, D.S. Influence of citric acid to aluminium nitrate molar ratio on the combustion synthesis of alumina–zirconia nanopowders. *J. Alloys Compd.* **2009**, *470*, L9–L12.
2. Wei, Z.; Li, H.; Zhang, X.; Yan, S.; Lv, Z.; Chen, Y.; Gong, M. Preparation and property investigation of CeO₂–ZrO₂–Al₂O₃ oxygen-storage compounds. *J. Alloys Compd.* **2008**, *455*, 322–326.
3. Wang, J.; Taleff, E.M.; Kovar, D. High-temperature deformation of Al₂O₃/Y-TZP particulate composites. *Acta Mater.* **2003**, *51*, 3571–3583.
4. Yin, W.; Meng, B.; Meng, X.; Tan, X. Highly asymmetric YSZ hollow fibre membranes. *J. Alloys Compd.* **2009**, *476*, 566–570.
5. Benzaid, R.; Chevalier, J.; Saadaoui, M. Fracture toughness, strength and slow crack growth in a ceria stabilized zirconia–alumina nanocomposite for medical applications. *Biomaterials* **2008**, *29*, 3636–3641.
6. Chevalier, J.; De-Aza, A.H.; Fantozzi, G.; Schehl, M.; Torrecillas, R. Extending the life time of ceramic orthopaedic implants. *Adv. Mater.* **2000**, *12*, 1619–1621.
7. Naglieri, V.; Gutknecht, D.; Garnier, V.; Palmero, P.; Chevalier, J.; Montanaro, L. Optimized Slurries for Spray Drying: Different Approaches to Obtain Homogeneous and Deformable Alumina-Zirconia Granules. *Materials* **2013**, *6*, 5382–5397.
8. Chevalier, J.; Gremillard, L.; Virkar, A.V.; Clarke, D.R. The tetragonal-monoclinic transformation in zirconia: Lessons learned and future trends. *J. Am. Ceram. Soc.* **2009**, *92*, 1901–1920.
9. Vernieuwe, K.; Lommens, P.; Martins, J.; Van Den Broeck, F.; Van Driessche, I.; De Buysser, K. Aqueous ZrO₂ and YSZ Colloidal Systems through Microwave Assisted Hydrothermal Synthesis. *Materials* **2013**, *6*, 4082–4095.
10. Chen, C.-C.; Hsiang, H.; Yen, F.S. Effects of aging on the phase transformation and sintering properties of coprecipitated Al₂O₃-ZrO₂ powders. *J. Ceram. Proc. Res.* **2008**, *9*, 13–18.
11. Suffner, J.; Lattemann, M.; Hahn, H.; Giebeler, L.; Hess, C.; Cano, I.G.; Dosta, S.; Guilemany, J.M.; Musa, J.C.; Locci, A.M.; et al. Microstructure Evolution During Spark Plasma Sintering of Metastable (ZrO₂–3 mol% Y₂O₃)–20 wt% Al₂O₃ Composite Powders. *J. Am. Ceram. Soc.* **2010**, *93*, 2864–2870.
12. Malka, I.E.; Danelska, A.; Kimmel, G. The Influence of Al₂O₃ Content on ZrO₂-Al₂O₃ Nanocomposite Formation—The Comparison between Sol-Gel and Microwave Hydrothermal Methods. *Mater. Today Proc.* **2016**, *3*, 2713–2724.
13. Hannink, R.H.J.; Kelly, P.M.; Muddle, B.C. Transformation toughening in zirconia—Containing ceramics. *J. Am. Ceram. Soc.* **2000**, *83*, 461–487.

14. Naglieri, V.; Palmero, P.; Montanaro, L.; Chevalier, J. Elaboration of Alumina-Zirconia Composites: Role of the Zirconia Content on the Microstructure and Mechanical Properties. *Materials* **2013**, *6*, 2090–2102.
15. Beitollahi, A.; Hosseini-Bay, Ć.H.; Sarpoolaki, Ć.H. Synthesis and characterization of Al₂O₃-ZrO₂ nanocomposite powder by sucrose process. *J. Mater. Sci. Mater. Electron.* **2010**, *21*, 130–136.
16. Septawendar, R.; Setiati, A.; Sutardi, S. Low-temperature calcination at 800 °C of alumina-zirconia nanocomposites using sugar as a gelling agent. *Ceram. Int.* **2011**, *37*, 3747–3754.
17. Shukla, S.; Seal, S.; Vij, R.; Bandyopadhyay, S. Effect of HPC and water concentration on the evolution of size, aggregation and crystallization of sol-gel nanozirconia. *J. Nanopart. Res.* **2002**, *4*, 553–559.
18. Begand, S.; Oberbach, T.; Glien, W. Corrosion behaviour of ATZ and ZTA ceramic. *Bioceramics* **2007**, *19*, 1227–1230.
19. Chuang, C.-C.; Hsiang, H.-I.; Hwang, J.S.; Wang, T.S. Synthesis and characterization of Al₂O₃-Ce_{0.5}Zr_{0.5}O₂ powders prepared by chemical coprecipitation method. *J. Alloys Compd.* **2009**, *470*, 387–392.
20. Opalinska, A.; Malka, I.; Dzwolak, W.; Chudoba, T.; Presz, A.; Lojkowski, W. Size dependent density of zirconia nanoparticles. *Beilstein J. Nanotechnol.* **2015**, *6*, 27–35.
21. Lojkowski, W.; Leonelli, C.; Chudoba, T.; Wojnarowicz, J.; Majcher, A.; Mazurkiewicz, A. High-Energy-Low-Temperature Technologies for the Synthesis of Nanoparticles: Microwaves and High Pressure. *Inorganics* **2014**, *2*, 606–619.
22. Wojnarowicz, J.; Chudoba, T.; Majcher, A.; Łojkowski, W. Microwaves applied to hydrothermal synthesis of nanoparticles. In *Microwave Chemistry*, 1st ed.; De Gruyter: Berlin, Germany; Boston, MA, USA, 2017; pp. 205–224, ISBN 9783110479935, doi:10.1515/9783110479935-012.
23. Wojnarowicz, J.; Opalinska, A.; Chudoba, T.; Gierlotka, S.; Mukhovskiy, R.; Pietrzykowska, E.; Sobczak, K.; Lojkowski, W. Effect of water content in ethylene glycol solvent on the size of ZnO nanoparticles prepared using microwave solvothermal synthesis. *J. Nanomater.* **2016**, *2016*, 2789871, doi:10.1155/2016/2789871.
24. Wojnarowicz, J.; Mukhovskiy, R.; Pietrzykowska, E.; Kusnieruk, S.; Mizeracki, J.; Lojkowski, W. Microwave solvothermal synthesis and characterization of manganese-doped ZnO nanoparticles. *Beilstein J. Nanotechnol.* **2016**, *7*, 721–732, doi:10.3762/bjnano.7.64.
25. Demazeau, G. Solvothermal Processes: Definition, Key Factors Governing the Involved Chemical Reactions and New Trends. *Z. Naturforsch.* **2010**, *65*, 999–1006.
26. Lóh, N.J.; Simão, L.; Justi, J.; De Noni, A.; Montedo, O.R.K. Effect of temperature and holding time on the densification of alumina obtained by two-step sintering. *Ceram. Int.* **2017**, *43*, 8269–8275.
27. Bowen, P.; Carry, C. From powders to sintered pieces: Forming, transformations and sintering of nanostructured ceramic oxides. *Powder Technol.* **2002**, *128*, 248–255.
28. Meng, F.; Liu, C.; Zhang, F.; Tian, Z.; Huang, W. Densification and mechanical properties of fine-grained Al₂O₃-ZrO₂ composites consolidated by spark plasma sintering. *J. Alloys Compd.* **2012**, *512*, 63–67.
29. Kong, Y.M.; Kim, H.E.; Kim, H.W. Production of aluminum-zirconium oxide hybridized nanopowder and its nanocomposite. *J. Am. Ceram. Soc.* **2007**, *90*, 298–302.
30. Zhuravlev, V.D.; Komolikhov, Y.I.; Ermakova, L.V. Correlations among sintering temperature, shrinkage, and open porosity of 3.5YSZ/Al₂O₃ composites. *Ceram. Int.* **2016**, *42*, 8005–8009.
31. Benaventea, R.; Salvadora, M.D.; Penaranda-Foix, F.L.; Pallone, E.; Borrell, A. Mechanical properties and microstructural evolution of alumina-zirconia nanocomposites by microwave sintering. *Ceram. Int.* **2014**, *40*, 11291–11297.
32. Lange, F.F. Transformation toughening Part 4: Fabrication, fracture toughness and strength of Al₂O₃-ZrO₂ composites. *J. Mater. Sci.* **1982**, *17*, 247–254.
33. Gutierrez-Mora, F.; Singh, D.; Chen, N.; Goretta, K.C.; Routbort, J.L.; Majumdar, S.H.; Dominguez Rodriguez, A. Fracture of composite alumina/yttria-stabilized zirconia joints. *J. Eur. Ceram. Soc.* **2006**, *26*, 961–965.
34. Zhang, F.; Li, L.F.; Wang, E.Z. Effect of micro-alumina content on mechanical properties of Al₂O₃/3Y-TZP composites. *Ceram. Int.* **2015**, *41*, 12417–12425.
35. Tang, D.; Lim, H.B.; Lee, K.J.; Lee, C.H.; Cho, W.S. Evaluation of mechanical reliability of zirconia-toughened alumina composites for dental implants. *Ceram. Int.* **2012**, *38*, 2429–2436.
36. Liu, G.; Xie, Z.; Wu, Y. Fabrication and mechanical properties of homogeneous zirconia toughened alumina ceramics via cyclic solution infiltration and in situ precipitation. *Mater. Des.* **2011**, *32*, 3440–3447.
37. Tang, D.; Lim, H.; Lee, K.; Ha, S.; Kim, K.; Cho, M.; Park, K.; Cho, W. Mechanical properties and high speed machining characteristics of Al₂O₃-based ceramics for dental implants. *J. Ceram. Process. Res.* **2013**, *14*, 610–615.

38. EN ISO 11885:2009-Water Quality. Determination of Selected Elements by Inductively Coupled Plasma Optical Emission Spectrometry (ICP-OES); International Organisation for Standardization: Geneva, Switzerland, 2008.
39. Rietveld, H.M. A profile refinement method for nuclear and magnetic structures. *J. Appl. Crystallogr.* **1967**, *2*, 65–71.
40. Young, R.A.; Sakthivel, A.; Moss, T.S.; Paiva-Santos, C.O. DBWS-9411—An upgrade of the DBWS*. programs for Rietveld refinement with PC and mainframe computers. *J. Appl. Crystallogr.* **1995**, *28*, 366–367.
41. Rodrigez-Carvajal, J. *Fullprof, Program for Rietveld Refinement*; Laboratoire Leon Brillouin (CEA-CNRS): Saclay, France, 1997.
42. ISO 22309:2011-Microbeam Analysis—Quantitative Analysis Using Energy-Dispersive Spectrometry (EDS) for Elements with An Atomic Number of 11 (Na) or Above; International Organisation for Standardization: Geneva, Switzerland, 2011.
43. ISO 12154:2014-Determination of Density by Volumetric Displacement. Skeleton Density by Gas Pycnometry; International Organisation for Standardization: Geneva, Switzerland, 2014.
44. ISO 9277:2010-Determination of the Specific Surface Area of Solids by Gas Adsorption—BET Method; International Organisation for Standardization: Geneva, Switzerland, 2010.
45. Nanopowder XRD Processor Demo. Available online: <http://science24.com/xrd/> (accessed on 10 September 2017).
46. Huang, X.; Chen, Z.; Gao, T.; Huang, Q.; Niu, F.; Qin, L.; Huang, Y. Hydrogen Generation by Hydrolysis of an Al/Al₂O₃—Composite Powder After Heat Treatment. *Energy Technol.* **2013**, *1*, 751–756.
47. Zhang, H.; Li, P.; Cui, W.; Liu, C.; Wang, S.; Zhenga, S.; Zhanga, Y. Synthesis of nanostructured γ -AlOOH and its accelerating behavior on the thermal decomposition of AP. *RSC Adv.* **2016**, *6*, 27235.
48. Sarkar, D.; Mohapatra, D.; Ray, S.; Bhattacharyya, S.; Adak, S.; Mitra, N. Synthesis and characterization of sol-gel derived ZrO₂. *Ceram. Int.* **2006**, *33*, 1275–1282.
49. Li, M.; Feng, Z.; Xiong, G.; Ying, P.; Xin, Q.; Li, C. Phase transformation in the surface region of zirconia detected by UV Raman spectroscopy. *J. Phys. Chem.* **2001**, *105*, 8107–8111.
50. Renuka, L.; Anantharaju, K.S.; Sharma, S.C.; Nagaswarupa, H.P.; Prashantha, S.C.; Nagabhushana, H.; Vidya, Y.S. Hollow microspheres Mg-doped ZrO₂ nanoparticles: Green assisted synthesis and applications in photocatalysis and photoluminescence. *J. Alloys Compd.* **2016**, *672*, 609–622.
51. Mao, Y.; Bai, J.; Zhang, M.; Zhao, H.; Sun, G.; Pan, X.; Zhang, Z.; Zhou, J.; Xie, E. Interface/defect-tunable macro and micro photoluminescence behaviours of Trivalent europium ions in electrospun ZrO₂/ZnO porous nanobelts. *Phys. Chem. Chem. Phys.* **2017**, *19*, 9223–9231.
52. Yobanny Reyes-López, S.; Saucedo Acuña, R.; López-Juárez, R.; Serrato Rodríguez, J. Analysis of the phase transformation of aluminum formate Al(O₂CH)₃ to α -alumina by Raman and infrared spectroscopy. *J. Ceram. Proc. Res.* **2013**, *14*, 627–631.
53. Liu, Y.; Cheng, B.; Wang, K.-K.; Ling, G.-P.; Cai, J.; Song, C.-L.; Han, G.-R. Study of Raman spectra for γ -Al₂O₃ models by using first-principles method. *Solid State Commun.* **2014**, *178*, 16–22.
54. Scheithauer, M.; Knozinger, H.; Vannicey, M.A. Raman Spectra of La₂O₃ Dispersed on γ -Al₂O₃. *J. Catal.* **1998**, *178*, 701–705.
55. Li, P.G.; Lei, M.; Tang, W.H. Raman and photoluminescence properties of α -Al₂O₃ microcones with hierarchical and repetitive superstructure. *Mater. Lett.* **2010**, *64*, 161–163.
56. Koltsov, I.; Przesniak-Welenc, M.; Wojnarowicz, J.; Rogowska, R.; Mizeracki, J.; Malysa, M.; Kimmel, G. Thermal and physical properties of ZrO₂-AlO(OH) nanopowders synthesised by microwave hydrothermal method. *J. Therm. Anal. Calorim.* **2017**, *131*, 2273–2284.
57. Scoton, A.; Chinelatto, A.; Chinelatto, A.L.; Ojaimi, C.L.; Ferreira, J.A.; Jesus E.M.; Pallone, A. Effect of sintering curves on the microstructure of alumina-zirconia nanocomposites. *Ceram. Int.* **2014**, *40*, 14669–14676.
58. Guimaraes, F.A.T.; Silva, K.L.; Trombini, V.; Pierri, J.J.; Rodrigues, J.A.; Tomasi, R.; Pallone, E.M.J.A. Correlation between microstructure and mechanical properties of Al₂O₃/ZrO₂ nanocomposites. *Ceram. Int.* **2009**, *35*, 741–745.
59. Lamouri, S.; Hamidouche, M.; Bouaouadja, N.; Belhouche, H.; Garnier, V.; Fantozzi, G.; Trellat, J.F. Control of the γ -alumina to α -alumina phase transformation for an optimized alumina densification. *Boletín Soc. Esp. Ceram. Vidr.* **2017**, *48*, 47–54.
60. Levin, I.; Brandon, D. Metastable Alumina Polymorphs: Crystal Structures and Transition Sequences. *J. Am. Ceram. Soc.* **1998**, *81*, 1995–2012.

61. Lee, J.; Jeon, H.; Oh, D.G.; Szanyi, J.; Kwak, J.H. Morphology-dependent phase transformation of γ -Al₂O₃. *Appl. Catal. A* **2015**, *500*, 58–68.
62. Zhou, R.-S.; Snyder, R.L. Structures and Transformation Mechanisms of the η , γ and θ Transition Aluminas. *Acta Cryst.* **1991**, *47*, 617–630.



© 2018 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).